

Low Cost Intermesh Mixing

Tilt Intermesh mixing versus Conventional Intermesh batch mixing

Kneader Machinery USA has set out to demonstrate that by mixing with their patent pending MXI-rotor technology the same and better mixing results can be achieved, with less than half the cost of a comparable sized conventional intermeshing rotor mixers.



Photo 573 – #3 MB Dispersion
(Conventional type Intermeshing rotor)

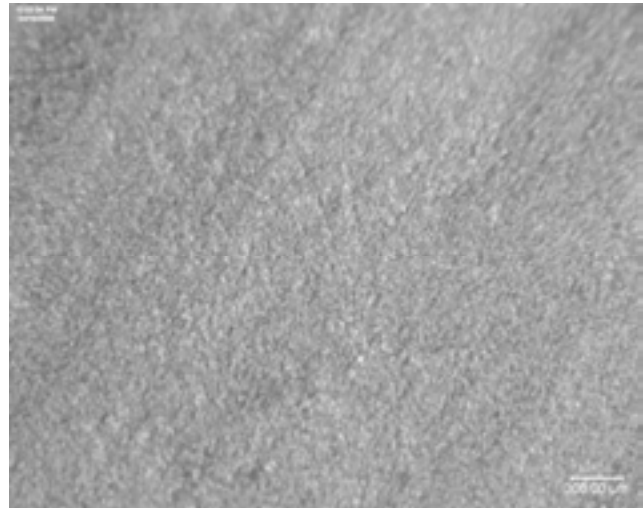


Photo 600 – #1 MB Dispersion
(KNEADER MXI-50 Intermeshing rotor)

There are generally two styles of mezzanine based internal mixers better known as “Tangential” rotor and “Intermeshing” rotor mixers. These mixers are well established in the market and utilized extensively in the rubber and plastics industries. OEM suppliers of these style mixers are Farrel, Kobelco and HF Rubber Machinery .

Kneader’s MXI series mixers operate on floor level saving thousands of dollars in mezzanine costs and installation. The new MXI rotor design delivers optimal mixing performance while in **most cases saving hundred’s of thousands of dollars in capital equipment costs.**

Based on test results it is clear that the MXI Intermesh rotors deliver equal if not superior compound dispersion and temperature control when compared to conventional intermesh mixers. Test results show physical properties are similar and Mooney scorch values are greatly improved with the MXI technology.

▪ TEST REPORT ▪

PN 77532

PO 2075

Compound Development

SUBJECT: Experimental comparison of mixing between a Conventional type batch mixer with Intermeshing rotors and a Kneader MXI-50 Intermeshing rotor tilt mixer.

The master batch compound selected for this comparison was specified as ASTM D3191. Compound selection, preparation, mixing and testing was performed or supervised by Akron Rubber Development Laboratories, Inc

The masterbatches from the Conventional type 50 liter mixer (Intermeshing rotors MB #3) and the MXI-50 Intermesh Tilt mixer (Intermeshing rotors compound #1) were mixed equally in time and temperature for the purpose of physical properties such as rheometer, Mooney scorch, tensile, modulus, elongation. Compound #2 was mixed using the MXI-50 Mixer, but the ingredient's were added all at one time and mixed two-minutes shorter to observe the difference in properties.

The cure was added to a small amount of each masterbatch material to yield the final properties. Photomicrographs were taken of the Masterbatch portion of the mix . Two mixes were produced using the MXI Tilt mixer and were labeled #1 and #2. One mix using the Conventional type intermeshing rotor mixer is labeled MB #3.

MB # 3

CONVENTIONAL TYPE 50 LITER INTERMESHING ROTOR MIXER

MIXING SPECIFICATION & DATA

STAGE I

Starting temperature 32°C (95°F), Rotor Speed 50 rpm, Ram Pressure 48 psi

TIME, minutes

0
1
2.5
4
5
5'40"

INGREDIENT or PROCEDURE

Polymer
Black, Sulfur, ZnO, Stearic acid
Sweep Slow to 24 rpm
Sweep 250°F, Slow to 15 rpm
Sweep 267°F, Slow to 13 rpm
dump 315°F

Mixed compounds placed on mill with roll temperatures @ 50° C (122° F). Cut three times each side, three end passes with the nip at 3/8 inch, 1 ½ minutes conveyer to second mill, 1 ½ sheet to dip tank and cool for 30 minutes.

MB #1
KNEADER MXI 50 LITER INTERMESHING ROTOR MIXER

MIXING SPECIFICATION & DATA

STAGE I

Starting temperature 32° C (95° F), Rotor Speed 50 rpm, Ram Pressure 35 psi

<u>TIME, minutes</u>	<u>INGREDIENT or PROCEDURE</u>
0	Polymer
1	Black, ZnO, Sulfur, Stearic Acid
1 ½ or 200°F	Sweep lower to 40 RPM
4 or 280°F	Sweep slow to 30 RPM
5	sweep 30 RPM
5' 40"	dump 320°F

Due to efficient cooling the rotor RPM did not have to be limited to 13 RPM to control the batch temperature rise.

Mixed compound was placed through a vertical, roller die to squeeze and cool the compound to a final sheet.

The following cure parameters were obtained and used to produce the tensile plaques from all of the masterbatches.

RHEOMETER DATA; ASTM D 2084-06

Tech Pro rheoTECH ODR
 160°C (320° F) 3° arc 100 inch lbs. 30 minute Chart Speed 100 cpm

	<u>MB#1</u>	<u>MB#2</u>	<u>MB#3</u>
Maximum Torque, M _H , lbf-inch	96.61	99.77	90.70
Minimum Torque, M _L , lbf-inch	18.26	19.30	18.72
Scorch Time, t _{s2} , minutes	4.08	3.89	3.22
Cure Time, t ₅₀ , minutes	10.81	10.53	7.79
Cure Time, t ₉₀ , minutes	17.18	16.60	12.82

MOONEY SCORCH, ASTM D 1646-06

Monsanto MV 2000 Viscometer
 121°C (250° F) Large Rotor 150 Range

	<u>MB#1</u>	<u>MB#2</u>	<u>MB#3</u>
Initial Viscosity, IV	99.70	112.20	111.70
Minimum Viscosity, MV	68.90	73.00	69.90
t ₅ , minutes/seconds	54.62	53.56	37.98

CURING & MOLDING DATA, ASTM D 3182-05

Test Plaque Size, inches	6 x 6 x 0.075
Cure Temperature,	145°C (293° F)
Cure Time, minutes	50

ORIGINAL PHYSICAL PROPERTIES, ASTM D 412-06a & DUROMETER HARDNESS D 2240

ASTM die C dumbbells tested @ 20 inch/minute crosshead speed
Dumbbells rested 24 hours @ 23°C (72° F) after curing and before testing
Durometer taken at instantaneous readings.

	<u>MB#1</u>	<u>MB#2</u>	<u>MB#3</u>
Ultimate Elongation, %	368	356	313
100% Modulus, psi	614	660	671
200% Modulus, psi	1861	1969	2079
300% Modulus, psi	3117	3220	3491
Tensile Strength, psi	3683	3729	3690
Durometer, Shore A	71	75	73

PHILLIPS DISPERSION RATING: ARDL PROCEDURE WI 3809

The samples were cut with a razor blade and pictures were taken at 30x magnification with an Olympus SZ60 Zoom Stereo Microscope interfaced with a PaxCam ARC digital camera and a Hewlett Packard 4600 Laser Jet color printer. The pictures of the samples were compared to a Phillips standard dispersion-rating chart having standards ranging from 1 (bad) to 10 (excellent). See Pictures for optical photomicrographs of the samples with embedded rating charts. A Phillips Dispersion Rating chart is also included for comparison.

Results

<u>Sample</u>	<u>Phillips Dispersion Rating</u>
#3 MB Uncured (see Photo 573)	7 (with Size 3 Agglomerate)
#1 MB Uncured (see Photo 600)	10
#2 MB Uncured (see Photo 602)	8

Prepared By: _____

Robert May


Approved By: _____

Jon F. Kopsky

573



Phillips Dispersion
Rating 7 with Size 3

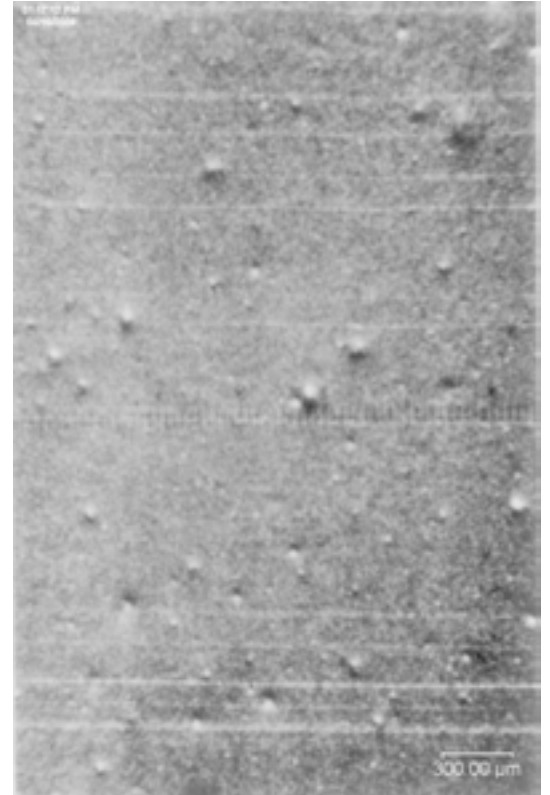

Phillips Dispersion
Rating 7

FIGURE A: Photo 573 – Kneader Machine P/N 77532 Sample
#3 MB Dispersion
(Conventional type Intermeshing rotor)


Don Kierstead
Akron Rubber Development Laboratories, Inc.
6/18/2008 4:04:03 PM



600



Phillips Dispersion
Rating 10

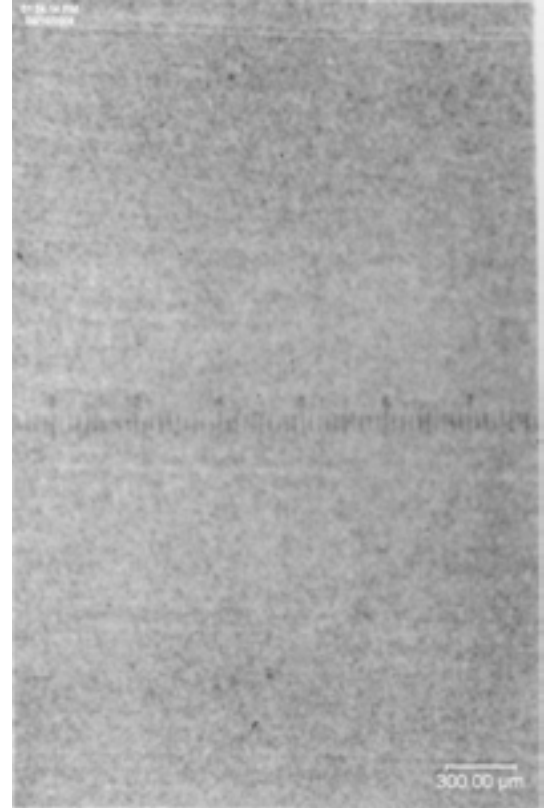

Phillips Dispersion
Rating 10


FIGURE E: Photo 600 – Kneader Machine P/N 77532
Sample #1 MB Dispersion
([KNEADER MXI-50 Intermeshing rotor](#))

Don Kierstead
Akron Rubber Development Laboratories, Inc.
6/18/2008 4:04:03 PM




Report created with
PAX-it for Windows

602

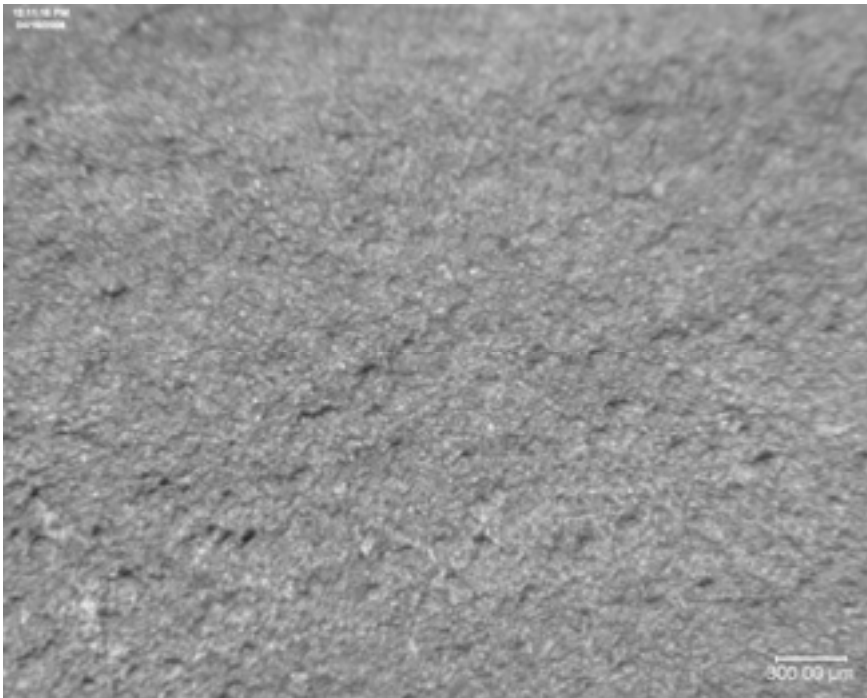

Phillips Dispersion
Rating 8

FIGURE G: Photo 602 – Kneader Machine P/N 77532
Sample #2 MB Dispersion
(KNEADER MXI-50 Intermeshing rotor)

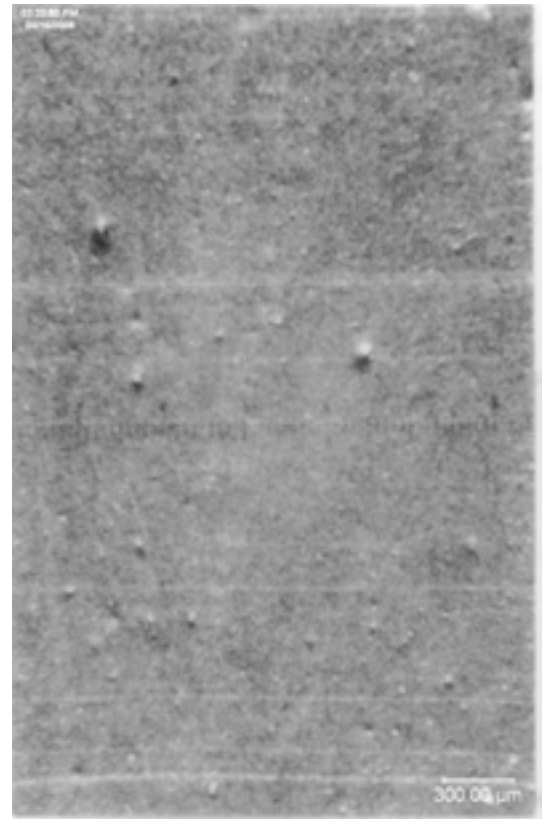


Phillips Dispersion
Rating 8

Don Kierstead
Akron Rubber Development Laboratories, Inc.

6/18/2008 4:04:03 PM



1Report created
with PAX-it for
Windows

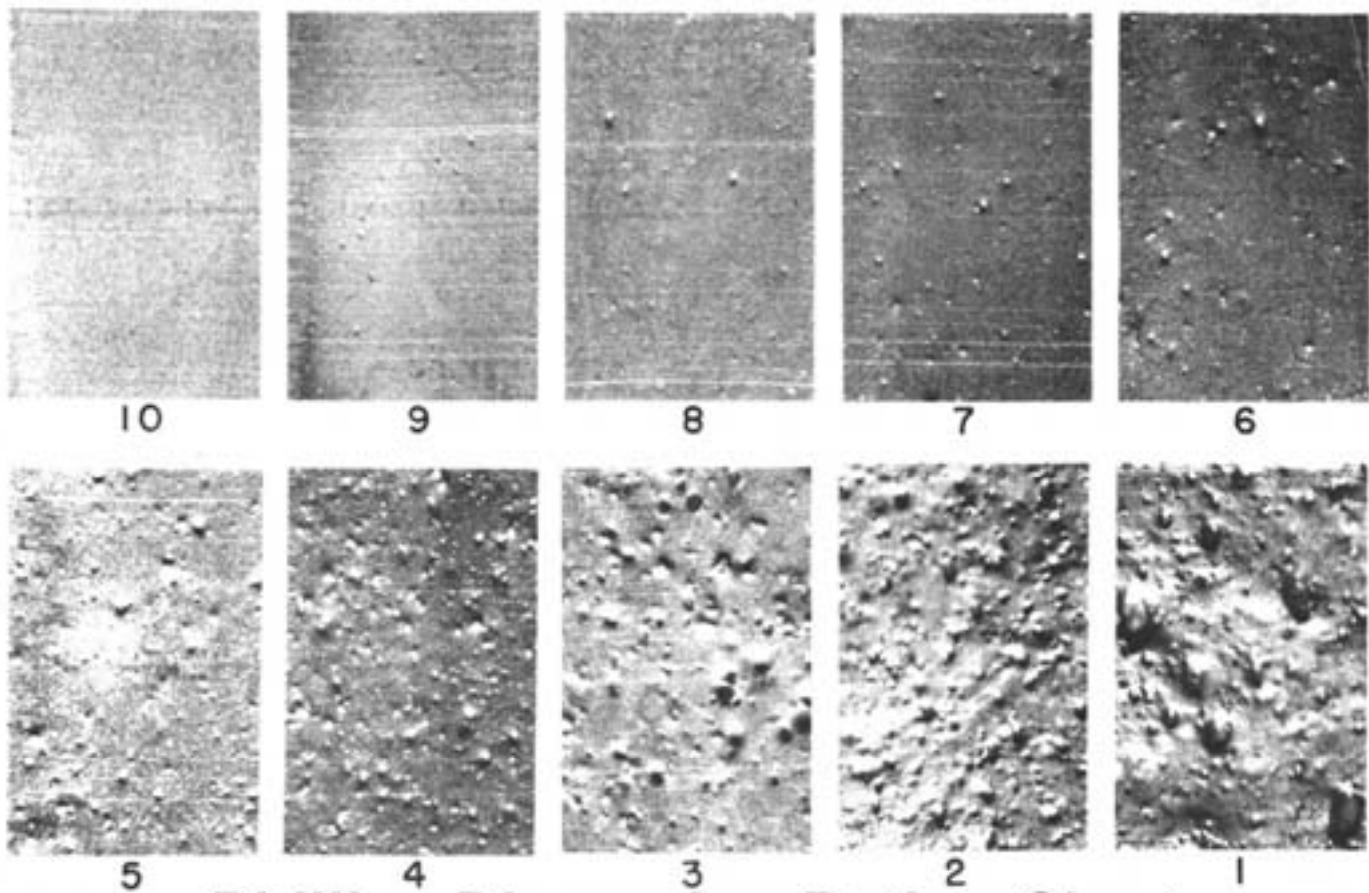

Phillips Dispersion Rating Chart
Photos @ 30X

Dept 10 on ardlc2:\Don's Reports\77532Phillips.doc

PHILLIPS DISPERSION RATING; ARDL PROCEDURE WI 3809

The samples were cut with a razor blade and pictures taken at 30x magnification with an Olympus SZ60 Zoom Stereo Microscope interfaced with a PaxCam ARC digital camera and a Hewlett Packard 4600 LaserJet color printer. The pictures of the samples were then compared to a Phillips standard dispersion-rating chart having standards ranging from 1 (bad) to 10 (excellent). See Photo's for optical photomicrographs of the samples with embedded rating charts. A Phillips Dispersion Rating is also included chart for comparison.

Results:

<u>Sample</u>	<u>Phillips Dispersion Rating</u>
#3 MB (see Photo 573)	7 (with Size 3 Agglomerate)
#1 MB (see Photo 600)	10
#2 MB (see Photo 602)	8

Akron Rubber Development Laboratory

ASTM D 1646

compuGRAPH V6.5.26

Report Date : Friday, April 11, 2008 10:54:25 AM

PROJECT NUMBER : PN77532


TEST DATE : Friday, April 11, 2008

CUSTOMER : Kneader Machine

COMPOUND I.D. :

Upper Die Temperature Setpoint : 121.0 C

Lower Die Temperature Setpoint : 121.0 C

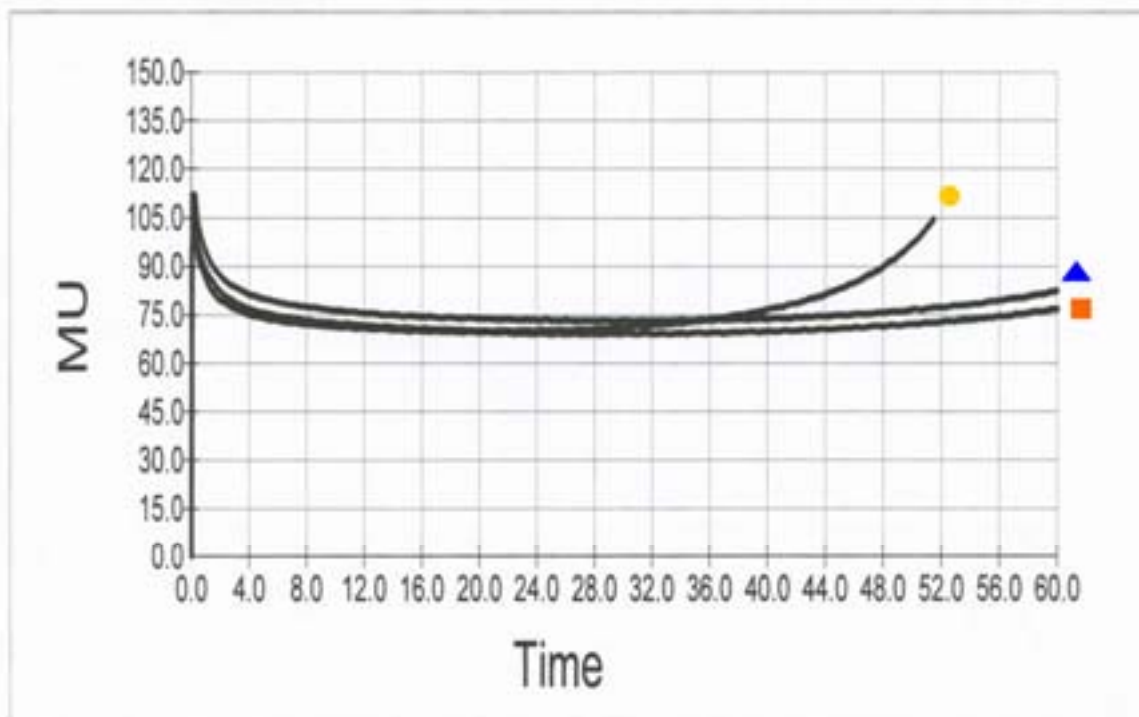

Test ID.		MI	ML	Ts5
#1MB	▲	99.70	68.90	54.62
#2MB	■	112.20	73.00	53.58
#3MB	●	111.70	69.90	37.98


Akron Rubber Development Laboratory

ASTM D 2084

compuGRAPH V6.5.26

Report Date : Friday, April 11, 2008 10:08:32 AM
 Compound ID : PN77532
 Mix Date : Friday, April 11, 2008
 Test Type : ASTM D 2084 - ODR
 Customer : Kneader Machine
 Degree Arc : 3

Upper Die Temperature Setpoint : 160.0 C
 Lower Die Temperature Setpoint : 160.0 C

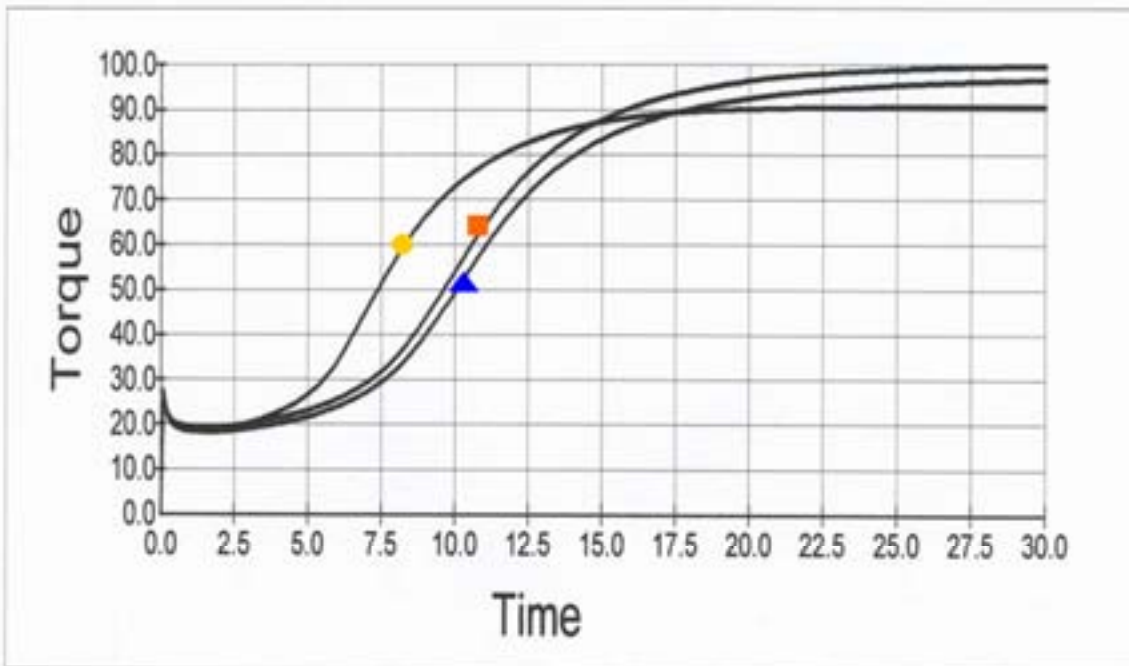

Test ID.	MH	ML	Tc50	Tc90	Ts2
#1MB ▲	96.61	18.26	10.81	17.18	4.08
#2MB ■	99.77	19.30	10.53	16.60	3.89
#3MB ●	90.70	18.72	7.79	12.82	3.22

Test Notes